

ORIGINAL ARTICLE

COMPARATIVE EVALUATION OF THE EFFECT OF TWO PLANT EXTRACT AND DENTURE CLEANSER ON THE STAINING AND ANTI-FUNGAL EFFICACY OF DENTURE BASE RESIN: AN IN VITRO STUDY

Prakhar Khurana¹

ABSTRACT

INTRODUCTION: Edentulism is the most common oral problem encountered in the human population and the commonest remedy to it is dentures. Natural products and essential oils are promising therapeutic tools for oral infection. The increasing awareness towards the varied uses of natural products has made them a popular alternative to synthetic materials. Therefore, a study is planned to evaluate and compare the antifungal efficacy of triphala and aloe vera when combined with denture cleansers on heat activated polymethyl methacrylate resin.

MATERIALS AND METHOD: In the present study 30 samples of polymethyl methacrylate resin of 20mm X 10mm X 2.5mm were fabricated. All the samples will be grouped into three groups of ten samples each and will be immersed in three test solutions for 8 hours daily for 30 days. The samples will be tested by spectrophotometer. Another test will be that all samples will be first inoculated with candida albicans mature biofilm, after which they will be dipped in the three solutions to observe the decrease in colony forming units per millimetre.

RESULTS: There was a statistically significant reduction in CFU/ml of both triphala and aloe vera solution. However, no statistically significant difference was found in color stability among the two groups.

CONCLUSION: Within the limitations of this study, it was found that both the denture cleansers showed a significant difference decrease in CFU/ml for anti-fungal efficacy on denture base resins when compared to control group. However, both the denture cleansers did not show a significant difference on the color stability of denture base resins.

KEYWORDS: Candida albicans, denture cleansers, aloe vera, triphala, staining, denture base resins

1. MDS (Prosthodontics), Clove Dental, New Delhi

Corresponding Author

Dr Prakhar Khurana

MDS (Prosthodontics), Clove Dental, New Delhi

INTRODUCTION

Oral hygiene is an important aspect in maintaining the well-being of an individual since ages. There is a lack of awareness regarding the maintenance of oral hygiene and management in elderly individuals. Denture-related stomatitis or Candida-associated denture-induced stomatitis is common condition seen in geriatric patients, where mild inflammation and redness of the oral mucosa occurs beneath a denture¹. The prevalence of candida has been observed to be around 60%–100%¹. It binds to dentures and if left to accumulate over a short period of time can cause mucosal inflammation and halitosis². Denture cleansers are a popular method used by denture wearers for cleaning. There are wide varieties of denture cleansers used to remove soft food and hard deposits of calculus and stains on denture base and teeth³. Deposits that form on the acrylic resin denture bases and on the teeth are assumed to be caused by the same mechanisms and substances that cause deposits on natural teeth, of which salivary calculus and tobacco tars are most common and most difficult to remove⁴. Natural products and essential oils are promising therapeutic tools for oral infection⁵. Aloe vera and triphala is the oldest medicinal plant ever known. Both has significant antimicrobial property¹. The increasing awareness towards the varied uses of natural products has made them a popular alternative to synthetic materials. Therefore, a study was planned to evaluate and compare the antifungal efficacy of triphala and aloe vera when combined with denture cleansers on heat activated polymethyl methacrylate resin.

MATERIALS AND METHOD

For the study, 30 samples of heat cure acrylic resin of 20mm X 10mm X 2.5mm dimensions were fabricated and were divided into three groups-

GROUP 1: denture cleanser + triphala solution in tap water

GROUP 2: denture cleanser + aloe vera solution in tap water

GROUP 3: denture cleanser in tap water (control)

For the fabrication of 30 samples, pre-fabricated metal

die of 21 mm x 11 mm x 2.6 mm was used and putty index was formed. Then modelling wax (DPI) was taken, melted and was poured into the putty index that was formed. The denture base resin patterns were then fabricated according to manufacturer's technique.

INITIAL COLOR EVALUATION

The initial color evaluation (CIE L*a*b* value) for each group was done by color spectrophotometer (SI. No-1004545, Model CM 2600D).

PREPARATION OF TEST SOLUTIONS

For evaluation of color stability of polymethyl methacrylate acrylic resin and efficacy of denture cleansers to remove *Candida albicans* biofilm, two test solutions were prepared. Plant extract test solution were prepared in the ratio of (1:10) by dissolving one tablet of fittydent denture cleanser in 100 ml tap water (to simulate environmental conditions) of 10 ml plant extract solution.

FINAL COLOR EVALUATION

The solution was prepared and placed in 30 small containers. Into each container one die of polymethyl methacrylate was dipped overnight (8 hours duration) for a period of 30 days in separate containers. After the treatment, each specimen was removed, cleaned and dried. The color change (AE) of each specimen was calculated as follows:

$$\Delta E [(\Delta L)^2 + (\Delta a)^2 + (\Delta b)^2]^{1/2}$$

REVIVAL OF CULTURE

Candida albicans pure strain powder was obtained. It was placed in a 40 mL container of BD Bactec Mycosis broth and cultured in a Bactec culture machine at 35°C for 48 hours. With the pour plate lawn culture method, 2ml of the revived *Candida albicans* suspension in the broth was plated on the Sabouraud dextrose Agar plate. Subculture was carried out in an incubator at 37°C for 48 hours.

METHOD FOR PREPARING THE STANDARDIZED CANDIDA SUSPENSION FOR BIOFILM FORMATION

With the use of a Densitometer, the *Candida* density was standardised to 2 x 10⁵ CFU/ml. Three millilitres of normal saline were placed in two polypropylene tubes. Colonies were picked from the culture plates and transferred to the tubes using loop. The densitometer was zeroed in order to standardise the density. The colony count was increased until the densitometer read

2 × 10⁵ CFU/ml. Sabouraud dextrose agar was put into three culture plates. When the agar was semisolid, 10 polymethyl methacrylate acrylic resin samples were inserted horizontally in each plate and left to freeze. In each culture plate, 1.5 mm of the standardised suspension was poured over the samples. All of the plates were incubated for 72 hours at 37°C.

POSITIVE CONTROL

After 72 hours, one sample was taken out, sonicated for 30 seconds, and the sonicated solution was serially diluted with pH buffer saline before being plated on a new agar plate with 2 ml of the suspension. At 37°C, this was incubated for 24 hours. The plate showed *Candida albicans* colonies after 24 hours, indicating that the yeast incubation process was successful.

TREATMENT OF SAMPLES

After 72 hours, all of the samples were removed from the plate and washed in PBS for 2 seconds to remove the loosely adherent *Candida*. It was then immersed in the test solutions for eight hours. Each specimen was gently washed in 2 mL of Phosphate Buffer Saline solution for 2 seconds in a sterile sonicator tube. Sonication at 8 W for 30 seconds was used to remove adherent bacteria from the sample. The sonicated solution was diluted in PBS and plated on a freshly prepared sabouraud dextrose agar plate with 1 ml of the suspension. The plates were incubated for 72 hours at 37°C in the incubator.

FINAL CULTURE COUNT

After 72 hours, 30 polypropylene tubes were numbered and filled with 3 mL distilled water. A loop of colony was harvested from the plate and suspended in the appropriate tubes. The densitometer was taken, and was zeroed. For the treated samples, all of the tubes were analysed for CFU/ml.

RESULTS

Table 1.1, 1.2 and Graph 1 shows that after treatment, except for Group III which showed an increase in colony count all other two groups showed a reduction in colony count. This reduction was maximum in Group I and minimum in Group III.

Table 2 shows a statistically significant intergroup difference with respect to change in mean colony forming unit in different groups. It was observed that change in the three groups were in negative direction. Among the three groups. Group 1 showed change values at the most negative value while Group III showed change values at the least negative order.

Table 1.1: Comparison of colony count in different groups after treatment

| S. NO. | GROUP I | GROUP II | GROUP III |
|-------------|----------|----------|-----------|
| 1. | 29090.91 | 67272.73 | 92727.27 |
| 2. | 25454.55 | 74545.45 | 85454.54 |
| 3. | 30909.09 | 61818.18 | 96363.64 |
| 4. | 36363.64 | 63636.36 | 94545.45 |
| 5. | 27272.73 | 72727.27 | 87272.73 |
| 6. | 25254.55 | 67272.73 | 98181.82 |
| 7. | 32727.27 | 63636.36 | 89090.91 |
| 8. | 30909.09 | 70909.09 | 85454.54 |
| 9. | 34545.45 | 74545.45 | 87272.73 |
| 10. | 27272.73 | 69090.91 | 92727.27 |
| Mean | 29980 | 68545 | 90909 |

Table 1.2: Comparison of mean colony count change from baseline in different groups after treatment

| | Group I | Group II | Group III |
|-------------|---------|----------|-----------|
| Mean | -170020 | -131455 | -109091 |
| SD | 3788 | 4620 | 4616 |
| Min | -174745 | -138182 | -114545 |
| Max | -163636 | -125455 | -101818 |
| Mean | -85.0 | -65.7 | -54.5 |
| SD | 1.9 | 2.3 | 2.3 |

Table 2: Analysis of variance for mean change in colony count in different groups

| | Sum of Squares | Df | Mean Square | F | Significance |
|--------------|------------------------|----|-----------------------|---------|--------------|
| Inter Groups | 3.0 X 10 ¹¹ | 3 | 1.0 X10 ¹¹ | 390.728 | <0.001 |
| Intra Group | 9.3 X 10 ⁹ | 36 | 2.5 X10 ⁹ | | |
| Total | 3.1 X 10 ¹¹ | | | | |

Table 3: Inter group comparison of change in colony count

| | Comparison | Absolute change | | % Change | | P-value |
|----|------------|-----------------|------|----------|------|---------|
| | | Mean | SE | Mean | SD | |
| 1. | I vs II | 228020 | 7199 | 114.01 | 3.60 | <0.001 |
| 2. | I vs III | 167091 | 7199 | 83.55 | 3.60 | <0.001 |
| 3. | II vs III | -60929 | 7199 | -30.46 | 3.60 | <0.001 |


Inter group comparison (Table 3) revealed a statistically significant difference for all the comparisons

Table 4 and Graph 2,3 and 4 shows distribution of mean and S.d. of color at positions L, b and a at two time interval of three groups

Table 5: On comparison (Inter group comparison) of means of color at positions L, b and a at two time

interval among three groups by one way ANOVA, there was a significant difference in means of color at position L on Final time, p=0.025, p<0.05. The remaining means of color were not significant p>0.05.

Table 6 shows the multiple comparison of means of color at positions L, b and a at two time interval among groups by Tukey’s HSD test. The mean difference of color Final L between group 2 and group 3 (5.0882) was significant, p<0.05. So the means of color Final L in group 2 (53.997) was significantly higher than group (348.909).

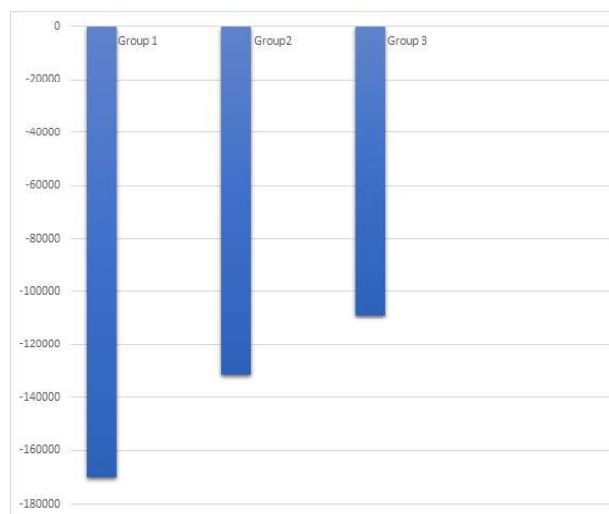


Graph 1: Comparison of mean colony count change in different groups after treatment

Table 7 showed the distribution of mean and S.d. of Color change “E of three groups. From Table 8, on comparison of mean of Color change “E among three groups by one way ANOVA, there was no significant difference in the means of Color change “E among three groups, p>0.05.


Table 9 showed the intra group comparison of means

Table 4: Change in lightnes ΔL (brightness) in different groups

| | Group | N | Mean | Std. Deviation | Std. Error | 95% Confidence Interval for Mean | | Minimum | Maximum |
|-----------|-------|----|--------|----------------|------------|----------------------------------|-------------|---------|---------|
| | | | | | | Lower Bound | Upper Bound | | |
| Initial L | I | 10 | 49.997 | 1.4140 | .4471 | 48.986 | 51.009 | 47.9 | 52.0 |
| | II | 10 | 50.249 | 1.6838 | .5325 | 49.045 | 51.454 | 47.9 | 53.1 |
| | III | 10 | 49.523 | 1.1049 | .3494 | 48.733 | 50.314 | 47.9 | 51.1 |
| Initial b | I | 10 | 5.192 | 1.1114 | .3515 | 4.397 | 5.987 | 2.7 | 6.1 |
| | II | 10 | 4.784 | .8731 | .2761 | 4.160 | 5.409 | 2.7 | 6.1 |
| | III | 10 | 4.784 | .8731 | .2761 | 4.160 | 5.409 | 2.7 | 6.1 |
| Initial a | I | 10 | 19.954 | 1.6198 | .5122 | 18.795 | 21.112 | 17.1 | 21.8 |
| | II | 10 | 19.128 | 1.8455 | .5836 | 17.808 | 20.449 | 16.2 | 20.6 |
| | III | 10 | 19.128 | 1.8455 | .5836 | 17.808 | 20.449 | 16.2 | 20.6 |
| Final L | I | 10 | 50.119 | 2.5039 | .7918 | 48.328 | 51.911 | 47.9 | 55.1 |
| | II | 10 | 53.997 | 6.5810 | 2.0811 | 49.290 | 58.705 | 47.9 | 67.7 |
| | III | 10 | 48.909 | .5848 | .1849 | 48.491 | 49.328 | 47.9 | 49.6 |
| Final b | I | 10 | 4.382 | .9905 | .3132 | 3.673 | 5.090 | 2.7 | 5.4 |
| | II | 10 | 4.161 | 1.5743 | .4979 | 3.035 | 5.287 | 1.6 | 6.1 |
| | III | 10 | 4.910 | 1.2188 | .3854 | 4.038 | 5.782 | 2.7 | 6.4 |
| Final a | I | 10 | 19.518 | 2.0563 | .6502 | 18.047 | 20.989 | 15.0 | 21.4 |
| | II | 10 | 17.154 | 3.9716 | 1.2559 | 14.312 | 19.995 | 10.8 | 21.2 |
| | III | 10 | 19.476 | 1.3296 | .4204 | 18.525 | 20.427 | 17.1 | 20.7 |

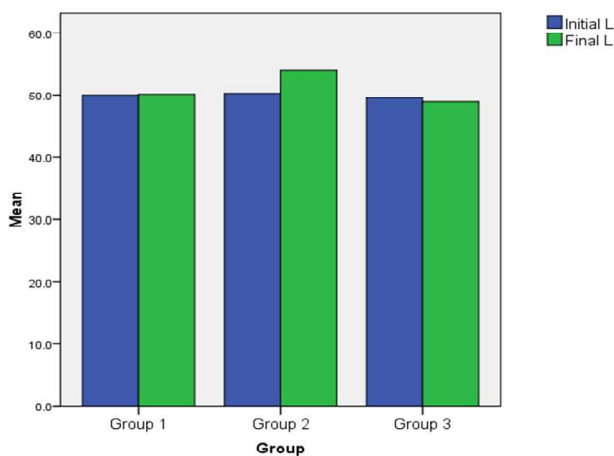

Graph 2: Distribution of means of color on position L at two time interval

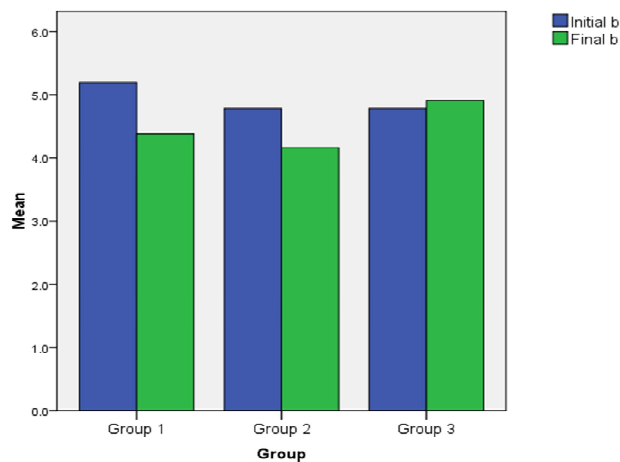

Graph 3: Distribution of means of color on position b at two time interval


of color between two time intervals on different positions of three groups paired t- test. The mean difference (.8106) of color between Initial b and Final b of group 1 was significant<0.05.

DISCUSSION

Oral microbial flora is comprised of numerous microorganisms like Streptococcus species, Staphylococcus species, Escherichia coli, Pseudomonas species and Candidal species^{6,7}. The most commonly found in denture wearers is the candida species^{2,8,9,10,11,12}. The present study was undertaken to see the effect in

combination of denture cleanser along with plant extract solution for polymethyl methacrylate resin.

Several studies ^{2,13,14,15,16,17} have evaluated the effect of denture cleansers on initial Candida (24-48 hours of biofilm) on denture base materials, however not much attention has been paid on the effect of these cleaning agents on Candida associated mature biofilm. The fungus grows in number, invades tissues, and causes illness over time, most likely as a result of the creation of more harmful cells aided by the phenotypic switching mechanism. Such qualities enable Candida albicans fungal cells to adapt quickly to changes in the host,

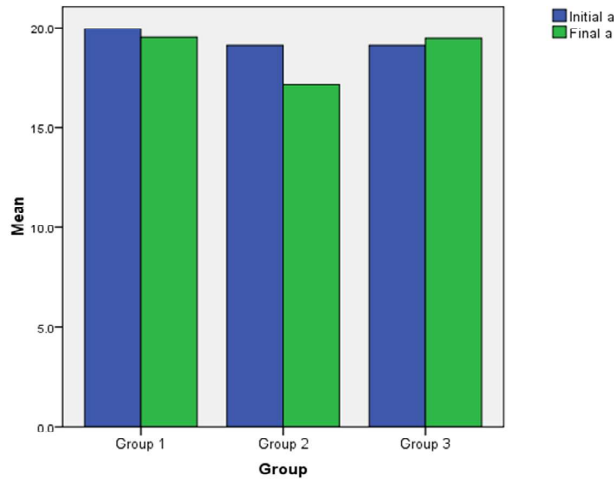

Graph 4: Distribution of means of color on position a at two time interval

such as evading immune system elements, acquiring antifungal resistance, and maximising colonisation and invasion of the host epithelial surface. Hence, in the present study, a time period of 72 hours¹⁸ has been given for mature biofilm formation so that the effectiveness of the denture cleansers can be evaluated.

Table 5 : Comparison (Inter group comparison) of means of color at positions L, b and a at two time interval among three groups by one way ANOVA

| ANOVA | | | | | | |
|-----------|-------------|----------------|----|-------------|-------|---------|
| | | Sum of Squares | df | Mean Square | F | P value |
| Initial L | Inter Group | 2.718 | 2 | 1.359 | .673 | .518 |
| | Intra Group | 54.499 | 27 | 2.018 | | |
| | Total | 57.218 | 29 | | | |
| Initial b | Inter Group | 1.109 | 2 | .554 | .603 | .555 |
| | Intra Group | 24.837 | 27 | .920 | | |
| | Total | 25.946 | 29 | | | |
| Initial a | Inter Group | 4.537 | 2 | 2.269 | .721 | .495 |
| | Intra Group | 84.921 | 27 | 3.145 | | |
| | Total | 89.459 | 29 | | | |
| Final L | Inter Group | 141.311 | 2 | 70.655 | 4.246 | .025* |
| | Intra Group | 449.287 | 27 | 16.640 | | |
| | Total | 590.598 | 29 | | | |
| Final b | Inter Group | 2.963 | 2 | 1.482 | .899 | .419 |
| | Intra Group | 44.506 | 27 | 1.648 | | |
| | Total | 47.470 | 29 | | | |
| Final a | Inter Group | 36.621 | 2 | 18.310 | 2.523 | .099 |
| | Intra Group | 195.924 | 27 | 7.256 | | |
| | Total | 232.545 | 29 | | | |

Table 6: Multiple Comparison of means of color at positions L, b and a at two time interval among groups by Tukey’s HSD test

| Dependent Variable | (I) Group vs (J) Group | Mean Difference (I-J) | Std. Error | P value | 95% Confidence Interval | |
|--------------------|------------------------|-----------------------|------------|---------------------|-------------------------|-------|
| | | | | | Min | Max |
| Initial L | 1 vs 2 | -.2519 | .6354 | .917 ^{NS} | -1.827 | 1.323 |
| | 1 vs 3 | .4742 | .6354 | .738 ^{NS} | -1.101 | 2.050 |
| | 2 vs 3 | .7261 | .6354 | .497 ^{NS} | -.849 | 2.301 |
| Initial b | 1 vs 2 | .4078 | .4289 | .614 ^{NS} | -.656 | 1.471 |
| | 1 vs 3 | .4078 | .4289 | .614 ^{NS} | -.656 | 1.471 |
| | 2 vs 3 | .0000 | .4289 | 1.000 ^{NS} | -1.063 | 1.063 |
| Initial a | 1 vs 2 | .8250 | .7931 | .559 ^{NS} | -1.141 | 2.791 |
| | 1 vs 3 | .8250 | .7931 | .559 ^{NS} | -1.141 | 2.791 |
| | 2 vs 3 | .0000 | .7931 | 1.000 ^{NS} | -1.966 | 1.966 |
| Final L | 1 vs 2 | -3.8780 | 1.8243 | .103 ^{NS} | -8.401 | .645 |
| | 1 vs 3 | 1.2102 | 1.8243 | .786 ^{NS} | -3.313 | 5.733 |
| | 2 vs 3 | 5.0882 | 1.8243 | .025* | .565 | 9.611 |
| Final b | 1 vs 2 | .2204 | .5742 | .922 ^{NS} | -1.203 | 1.644 |
| | 1 vs 3 | -.5286 | .5742 | .632 ^{NS} | -1.952 | .895 |
| | 2 vs 3 | -.7490 | .5742 | .405 ^{NS} | -2.173 | .675 |
| Final a | 1 vs 2 | 2.3645 | 1.2047 | .141 ^{NS} | -.622 | 5.351 |
| | 1 vs 3 | .0421 | 1.2047 | .999 ^{NS} | -2.945 | 3.029 |
| | 2 vs 3 | -2.3224 | 1.2047 | .150 ^{NS} | -5.309 | .665 |

Table 7: Distribution of mean and S.d. of Color change “E of three groups

| Group | N | Mean | Std. Deviation | Std. Error | 95% Confidence Interval for Mean | | Minimum | Maximum |
|-------|----|--------|----------------|------------|----------------------------------|-------------|---------|---------|
| | | | | | Lower Bound | Upper Bound | | |
| 1 | 10 | 2.0394 | 1.60703 | .50819 | .8898 | 3.1890 | .00 | 4.45 |
| 2 | 10 | 5.5759 | 6.44404 | 2.03778 | .9661 | 10.1857 | .00 | 15.23 |
| 3 | 10 | 2.6263 | 1.97781 | .62544 | 1.2115 | 4.0412 | .53 | 4.70 |

Table 8: Comparison of mean of Color change “E among three groups by one way ANOVA

| ANOVA | | | | | |
|----------------|----------------|----|-------------|-------|--------------------|
| ΔE | | | | | |
| | Sum of Squares | df | Mean Square | F | P value |
| Between Groups | 71.838 | 2 | 35.919 | 2.244 | .125 ^{NS} |
| Within Groups | 432.179 | 27 | 16.007 | | |
| Total | 504.017 | 29 | | | |

Shetty et al¹⁹ and Shireen et al²⁰ evaluated the effect of aloe vera on anti-fungal efficacy and found to be effective. The results were consistent with the Iseri et al¹⁰ and however he compared the efficacy against mouth rinses. The effect was similar with Ferreira et al²¹ when compared with multispecies biofilm.

The result of the present study are in consistent with several authors^{22,23,24} in which the authors did not detect any color changes in the use of denture cleansers. Whereas, the results are not consistent with several authors^{13,25,26,27} in which the authors detected a significant color change. The difference in results might be due to the fact that the samples were immersed with denture cleansers for ninety days, whereas in this study the time period selected was thirty days.

Only chemical cleansing can be considered in the present study, Chemical cleansing could be a good choice

for the elderly too, who require adjunctive measures to clean their dentures. Several studies^{28,29} showed combination methods was more effective than chemical cleansing alone.

Sodium perborate is a peroxide type denture cleanser. When dissolved in water, it forms a solution of hydrogen peroxide. This type of cleanser combines alkaline detergents to reduce surface tension and chemicals that release oxygen from the solution. The oxygen bubbles exert a mechanical cleansing effect³⁰. The denture cleansers that have been selected in the present study is evaluated for its effectiveness against *Candida albicans* mature biofilm by dipping the polymethyl methacrylate acrylic resin samples with the Candidal biofilm in it for 8 hours^{8,31}. The literature has stated various time intervals for evaluating the same³².

In this study out of the two plant extract solutions triphala solution showed increase in anti-fungal efficacy than aloe vera solution when compared to the control group whereas there was no significant difference in the color stability however out of the two solutions aloe vera showed better stability than triphala solution when compared to the control group.

The present study provides some clinical implications which are of benefit to the denture wearers as well as for the clinician. For use by patients with severe denture stomatitis, a denture cleanser with highest

Table 9: Intra group comparison of means of color between two time intervals on different positions of three groups paired t- test

| Group | | Paired Differences | | | | t | df | P value | |
|-------|---------------------|--------------------|----------------|-----------------|---|--------|--------|---------|--------------------|
| | | Mean | Std. Deviation | Std. Error Mean | 95% Confidence Interval of the Difference | | | | |
| | | | | | Lower | | | | Upper |
| 1 | Initial L - Final L | -.1220 | 1.9228 | .6081 | -1.4975 | 1.2535 | -.201 | 9 | .845 ^{NS} |
| | Initial b - Final b | .8106 | 1.0735 | .3395 | .0427 | 1.5785 | 2.388 | 9 | .041 [*] |
| | Initial a - Final a | .4355 | 1.1819 | .3738 | -.4100 | 1.2810 | 1.165 | 9 | .274 ^{NS} |
| 2 | Initial L - Final L | -3.7481 | 5.9601 | 1.8847 | -8.0117 | .5155 | -1.989 | 9 | .078 ^{NS} |
| | Initial b - Final b | .6232 | 1.5862 | .5016 | -.5115 | 1.7579 | 1.242 | 9 | .245 ^{NS} |
| | Initial a - Final a | 1.9750 | 4.2021 | 1.3288 | -1.0310 | 4.9810 | 1.486 | 9 | .171 ^{NS} |
| 3 | Initial L - Final L | .6140 | 1.4893 | .4709 | -.4514 | 1.6794 | 1.304 | 9 | .225 ^{NS} |
| | Initial b - Final b | -.1258 | 1.3634 | .4311 | -1.1011 | .8495 | -.292 | 9 | .777 ^{NS} |
| | Initial a - Final a | -.3474 | 2.6322 | .8324 | -2.2304 | 1.5356 | -.417 | 9 | .686 ^{NS} |

ability of biofilm removal should be recommended like combination of denture cleanser and triphala solution and if color stability is more important for the patient than a combination of denture cleanser and aloe vera solution is recommended.

The limitations of this study was that mixed microbial biofilms were not assessed. In the oral cavity, microorganisms exist in polymicrobial communities and different species interact in a complex manner to modulate biofilm nature. Also, this study did not simulate the oral environment conditions in which the *Candida* biofilms develop on denture. Time of dipping the samples into denture cleansers was another factor which would have been varied to longer

durations to see the long term effect. Also, other cleansing aids like brushing or ultrasonic cleansing were not used to assess the efficacy of denture cleansers.

Hence, further studies should look at the in vivo as well as in vitro response of mixed communities with longer time intervals and using other denture cleaning aids also.

CONCLUSION

The following conclusions can be drawn:

1. Both the plant extract solutions showed significant decrease in CFU/ml for *Candida albicans* biofilm on denture base resins when compared to control group.
2. Among the two plant extract denture cleansers used, the most effective in reduction of CFU/ml for *Candida albicans* was triphala solution followed by aloe vera solution.
3. The plant extract were not significantly effective in removing stains from heat cure denture acrylic resins on short term basis.

REFERENCE

1. **Isadkar YS, Palaskar SJ, Narang B, Bartake AR.** Aloe vera as denture cleanser. *J Dent Allied Sci* 2018;7:23-6
2. **Harrison Z, Johnson A, Douglas CWI.** An in vitro study into the effect of a limited range of denture cleaners on surface roughness and removal of *Candida albicans* from conventional heat-cured acrylic resin denture base material. *J Oral Rehabil* 2004;31:460-7.
3. **Salem SAL, Al-Khafaji AMA.** The effect of prepared denture cleansers on some physical properties of stained acrylic resin denture base material cured by two different techniques. *J Baghdad Coll Dent* 2006;18(2):1-8.
4. **Nicholsan RJ, Stark MM, Scott HE.** Calculus and stain removal from acrylic resin dentures. *J Prosthet Dent* 1968 Oct;20(4):326-9.

5. **Anjum R, Dhaded SV, Joshi S, Sajjan CS, Konin P, Reddy Y.** Effect of plant extract denture cleansing on heat-cured acrylic denture base resin: An in vitro study. *J Indian Prosthodont. Soc* 2017;17:401-5.
6. **Banu F, Jeyapalan K, V AK, Modi K.** Comparison of Colour Stability Between Various Denture Base Resins on Staining and Denture Cleansing Using Commercially Available Denture Cleansers. *Cureus.* 2020Jan 19;12(1):1-2.
7. **Srinivasan M, Gulabani M.** A microbiological evaluation of the use of denture cleansers in combination with an oral rise in complete denture patients. *LJDR* 2010;21(3):353-356.
8. **Paranhos, Helena & Orsi, Iara & Zaniquelli, Osvaldo & Zuccolotto, Maria & Magalhães, Fabrício.** Effect of chemical denture cleansers on flexural resistance and color changes of microwave-polymerized acrylic resins. *Braz. J. Oral Sci* 2008;7(26):1580-4.
9. **Ferreira MA, Pereira-Cenci T, Rodrigues de Vasconcelos LM, Rodrigues-Garcia RC, Del Bel Cury AA.** Efficacy of denture cleansers on denture liners contaminated with *Candida* species. *Clin Oral Investig.* 2009 Jun;13(2):237-42.
10. **I'eri U, Uludamar A, Ozkan YK.** Effectiveness of different cleaning agents on the adherence of *Candida albicans* to acrylic denture base resin. *Gerodontology.* 2011 Dec;28(4):271-6.
11. **Oliveira VMB, Lucena SC, Garcia RCMR, Cury AADB.** Effect of a denture cleanser on the concentration of volatile sulphur compounds and denture biofilm in institutionalized elderly. *Gerodontology* 2011;28:134-9
12. **Lucena-Ferreira SC, Ricomini-Filho AP, Silva WJ, Cury JA, Cury AA.** Influence of daily immersion in denture cleanser on multispecies biofilm. *Clin Oral Investig.* 2014 Dec;18(9):2179-85
13. **Peracini A, Davi LR, de Queiroz Ribeiro N, de Souza RF, Lovato da Silva CH, de Freitas Oliveira Paranhos H.** Effect of denture cleansers on physical properties of heat-polymerized acrylic resin. *J Prosthodont Res.* 2010 Apr;54(2):78-83.
14. **Nalbant AD, Kalkanci A, Filiz B, Kustimur S.** Effectiveness of different cleaning agents against the colonization of *Candida* spp and the in vitro detection of the adherence of these yeast cells to denture acrylic surfaces. *Yonsei Med J.* 2008 Aug 30;49(4):647-54.
15. **Salman M. Saleem S.** Effect of different denture cleansers solution on some mechanical and physical properties of nylon and acrylic denture base *J Bagh Coll Dentistry* 2011;23:19-24.
16. **Lucena-Ferreira SC, Ricomini-Filho AP, Silva WJ, Cury JA, Cury AA.** Influence of daily immersion in denture cleanser on multispecies biofilm. *Clin Oral Investig.* 2014 Dec;18(9):2179-85.
17. **Dhamande MM, Pakhan AJ, Thombare RU, Ghodpage SL.** Evaluation of efficacy of commercial denture cleansing agents to reduce the fungal biofilm activity from heat polymerized denture acrylic resin: An in vitro study.

- Contemp Clin Dent. 2012 Apr;3(2):168-72.
18. **Faot F, Cavalcanti YW, Mendonça e Bertolini Md, Pinto Lde R, da Silva WJ, Cury AA.** Efficacy of citric acid denture cleanser on the *Candida albicans* biofilm formed on poly(methyl methacrylate): effects on residual biofilm and recolonization process. *BMC Oral Health*. 2014 Jun 23;14:77.
 19. **Shetty PJ, Hegde V, Gomes L.** Anticandidal efficacy of denture cleansing tablet, Triphala, Aloe vera, and Cashew leaf on complete dentures of institutionalized elderly. *J Ayurveda Integr Med*. 2014 Jan;5(1):11-4.
 20. **Shireen F, Manipal S, Prabhu D.** Anti-fungal activity of Aloe vera: In vitro stud. *SRM Journal of Research in Dental Sciences*. 2015;6:92.
 21. **Lucena-Ferreira SC, Ricomini-Filho AP, Silva WJ, Cury JA, Cury AA.** Influence of daily immersion in denture cleanser on multispecies biofilm. *Clin Oral Investig*. 2014 Dec;18(9):2179-85.
 22. **Sato S, Cavalcante MR, Orsi IA, Paranhos Hde F, Zaniquelli O.** Assessment of flexural strength and color alteration of heat-polymerized acrylic resins after simulated use of denture cleansers. *Braz Dent J*. 2005;16(2):124-8.
 23. **Durkan R, Ayaz EA, Bagis B, Gurbuz A, Ozturk N, Korkmaz FM.** Comparative effects of denture cleansers on physical properties of polyamide and polymethyl methacrylate base polymers. *Dent Mater J*. 2013;32(3):367-75.
 24. **Banu F, Jeyapalan K, V AK, Modi K.** Comparison of Colour Stability Between Various Denture Base Resins on Staining and Denture Cleansing Using Commercially Available Denture Cleansers. *Cureus*. 2020Jan 19;12(1):1-2.
 25. **Moon A, Powers JM, Kiat-Amnuay S.** Color stability of denture teeth and acrylic base resin subjected daily to various consumer cleansers. *J Esthet Restor Dent*. 2014 Jul-Aug;26(4):247-55.
 26. **Porwal A, Khandelwal M, Punia V, Sharma V.** Effect of denture cleansers on color stability, surface roughness, and hardness of different denture base resins. *J. Indian Prosthodont. Soc*. 2017 Sep;17:61-7.
 27. **Sethi S, Singhal R, Agarwal SK, Hasan S.** Comparative evaluation of stain removal and flexural strength of denture base acrylic resin by using two different denture cleansers: an in – vitro study. *Int. J. Sci. Res*. 2017;6(6):4-6.
 28. **Cruz PC, Andrade IM, Peracini A, Souza-Gugelmin MC, Silva-Lovato CH, de Souza RF, Paranhos Hde F.** The effectiveness of chemical denture cleansers and ultrasonic device in biofilm removal from complete dentures. *J Appl Oral Sci*.
 29. **Baba Y, Sato Y, Owada G, Minakuchi S.** Effectiveness of a combination denture-cleaning method versus a mechanical method: comparison of denture cleanliness, patient satisfaction, and oral health-related quality of life. *J Prosthodont Res*. 2018 Jul;62(3):353-358.
 30. **Mathai JR.** Comparison of efficacy of sodium hypochlorite with sodium perborate in removal of stains from heat-cured clear acrylic resin. *J. Indian Prosthodont. Soc* 2009 Jan;9(1):6-12.
 31. **Kumar M N, Thippeswamy HM, Raghavendra Swamy K N, Gujjari AK.** Efficacy of commercial and household denture cleansers against *Candida albicans* adherent to acrylic denture base resin: An in vitro study. *Indian J Dent Res* 2012;23:39-42.
 32. **Al-Huraishi H, Moran J, Jagger R and MacDonald E.** Evaluation of stain removal and inhibition properties of eight denture cleansers: an in vitro study. *Gerodontology* 2013, 30:10-17.